

Original Article

Effect of sintering parameters on the mechanical properties of monolithic zirconia

Caner Öztürk^{1*} • Gülşen Can²

¹Department of Prosthodontics, Faculty of Dentistry, Hatay Mustafa Kemal University, Hatay, Turkey

²Department of Prosthodontics, Faculty of Dentistry, İstanbul Aydın University, İstanbul, Turkey

*Corresponding Author; E-mail: caner_ozturk86@hotmail.com

Received: 28 August 2019; Accepted: 23 December 2019

J Dent Res Dent Clin Dent Prospect 2019; 13(4):247-252|doi: 10.15171/joddd.2019.038

This article is available from: <https://joddd.tbzmed.ac.ir>

© 2019 Öztürk and Can This is an Open Access article published and distributed by Tabriz University of Medical Sciences under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Abstract

Background. Zirconia restorations with high mechanical properties are the current treatment options for fixed restorations with advantages of high biocompatibility and low pulp irritation. Although the effect of sintering time and temperature on the optical and mechanical properties of zirconia core material were investigated, the effect of these parameters on the translucent monolithic zirconia is still uncertain. This study aimed to evaluate the effect of the changes in sintering temperature and holding time on the mechanical and structural properties of monolithic zirconia.

Methods. Totally, 340 self-colored (A2) zirconia specimens from two different monolithic zirconia groups (n=170) were prepared, measuring 15.5×12.5×1.2 mm. Then, 17 subgroups (n=10), including the control groups, were sintered according to sintering parameters. XRD analysis was used to determine phase transformations. The surface roughness of the specimens was evaluated using profilometry, and the flexural strength of the specimens was evaluated by the three-point bending test. The data were analyzed using three-way ANOVA and post hoc multiple comparison test with Bonferroni correction ($\alpha=0.05$) at a significance level of 0.05. Independent-samples t-test was used to compare the subgroups between the control groups ($P<0.05$).

Results. No tetragonal-to-monoclinic phase transformation was observed in the groups. Changes in the sintering parameters did not significantly affect the surface roughness and flexural strength of monolithic zirconia. Surface roughness values for all the subgroups were above the clinically critical limit.

Conclusion. According to the results of this study, changes in the sintering parameters did not affect the surface phase transformation, surface roughness, and flexural strength of monolithic zirconia.

Key words: Flexural strength, monolithic zirconia, sintering parameters, surface roughness.

Introduction

Concurrent with the development of CAD/CAM technology, zirconia has been widely used in the

dental field due to its excellent mechanical properties, high biocompatibility, and low allergic potential.¹ Zirconia, without a glass component, is a polycrystalline

polymorphic material and occurs in three forms of monoclinic, tetragonal, and cubic. Pure zirconia occurs in monoclinic phase at room temperature, becomes tetragonal between 1170°C and 2370°C, and the cubic phase is stable up to the melting point of 2680°C.² The yttrium-stabilized tetragonal zirconia polycrystalline (Y-TZP), the most commonly used zirconia in dentistry and stable with yttrium in nanometers at room temperature, could be obtained by alloying zirconia with 2–3% of yttrium oxide.^{3,4}

In previous studies, the flexural strength of zirconia ceramics varied between 608 and 1540 MPa, and these differences occur depending on sintering parameters, surface treatments, and microstructure.⁵⁻⁷ Stawarczyk et al⁷ reported that an increase in the sintering temperature resulted in a decrease in the flexural strength of zirconia. In contrast, some studies reported that sintering parameters did not affect the flexural strength of zirconia ceramics.^{8,9}

According to the literature, the critical smoothness for plaque accumulation is 0.2 µm.^{10,11} Heintze et al¹² reported that rough surfaces reduce the fracture resistance of the material, and changes in surface roughness affect the wear properties of zirconia. In clinical applications, the grinding procedures made by the dentist also directly affect the wear properties of zirconia. Additionally, it has been reported that changes in surface roughness also stimulate phase transformation.¹³ Preis et al¹⁴ reported that the polishing process reduces surface roughness and phase transformations on the zirconia surface. Currently available zirconia materials are generally sintered between 1350°C and 1600°C, and yttrium is incorporated into the structure at high sintering temperatures.¹⁵ However, sintering temperatures higher than 1600°C cause excessive grain growth and increase porosity. Besides, it was observed that the mechanical and optical properties of the zirconia were not sufficient at sintering temperatures of <1400°C.^{3,7} The degradation of zirconia at low temperatures and the strength of the material depend on many factors, including the amount of the stabilizing oxide, the distribution of the stabilizer, the phase composition, the particle size and distribution, etching and surface treatments, and the presence of the secondary phases. Although these factors are independent, they are mainly affected by sintering parameters, which have been considered as predominant factors to obtain stable zirconia.¹⁶

Zirconia is used as an infrastructure due to its high opacity, and the main disadvantage of zirconia restorations is chipping in veneering ceramics. To overcome the chipping problem, the use of monolithic zirconia restorations, which can be used without

veneering ceramics, has gained popularity. In addition, with monolithic zirconia blocks, it is possible to obtain more translucent and aesthetic restorations without veneering ceramics.¹⁶ Additionally, as a result of high flexibility and fracture strength, monolithic zirconia can be used even in cases where the interocclusal distance is insufficient in the posterior region.^{3,7}

Changes in sintering parameters affect the properties and microstructure of zirconia.¹⁷ However, the effect of sintering parameters on monolithic zirconia, directly related to oral conditions, is still uncertain.^{8,7,18} Therefore, this study investigated the effect of sintering parameters on the microstructure, surface roughness, and flexural strength of monolithic zirconia materials. The null hypothesis of the study was that sintering parameters do not affect the microstructure, surface roughness, and flexural strength of the translucent monolithic zirconia.

Methods

In this *in vitro* study, two different commercially available pre-sintered, self-colored (A2) translucent monolithic zirconia materials (Group TZI; Incoris TZI C, Sirona Dental Systems GmbH, Bensheim, Germany) (Group Up; Upcera, Shenzhen Upcera Co., Ltd, Shenzhen, China) were used. Totally, 340 samples ($n=170$) with a dimension of $19 \times 15.5 \times 1.6 \pm 0.05$ mm were prepared from pre-sintered blocks using a precision cutting machine (Microcut 201 Mekto Instruments Inc., Istanbul, Turkey). All the samples in each group were randomly divided into 16 subgroups according to sintering temperature (1400°C, 1450°C, 1500°C, and 1600°C) and holding time (30, 60, 120, and 240 min) for each group ($n=10$). Additionally, one subgroup, sintered according to the manufacturer's instructions, was defined as the control group ($n=10$) (Table 1). The heating and cooling rates were set to 10°C/min. The sintering furnace (InFire HTC Speed, Sirona Dental Systems GmbH Bensheim, Germany) was calibrated before each sintering process according to the manufacturer's instructions. The temperature changes were checked by the internal thermometer of the sintering furnace. After the sintering process, the dimension of all samples was measured using a digital micrometer, and the final dimension of the samples was $15.5 \times 12.5 \times 1.2 \pm 0.03$ mm. Then, all the samples were thermocycled in a thermal cycling machine (Thermocycler THE-1100 SD Mechatronic GMBH, Feldkirchen, Germany), consisting of 10000 cycles at 5°C and 55°C with 20-second dwell time. After the thermocycling procedure,

Table 1. Sample size of the subgroups in terms of the holding time and sintering temperature

Group TZI (n)	30 min.	60 min.	120 min.	240 min.	Total
1400°C	10	10	10	10	40
1450°C	10	10	10	10	40
1500°C	10	10	10	10	40
1600°C	10	10	10	10	40
Control Group					10
Total					170
Group UP (n)	30 min.	60 min.	120 min.	240 min.	Total
1400°C	10	10	10	10	40
1450°C	10	10	10	10	40
1500°C	10	10	10	10	40
1600°C	10	10	10	10	40
Control Group					10
Total					170

all the groups were ultrasonically cleaned with isopropanol solution and kept at room temperature in dry air.

Microstructural analysis (XRD Analysis)

The effect of sintering temperature and holding time on the phase composition and t-m transformation were crystallographically examined using a diffractometer (Bruker D8 Advance, Bruker AXS GmbH, Karlsruhe, Germany) on three randomly selected samples from each group. All the samples were subjected to Cu K(alpha) radiation. The voltage and current were set to 40 kVp and 40 mA, respectively. Diffraction profiles were recorded within a range of -10 to 90°, a continuous $\theta/2\theta$ scan with a step size of 0.05°, and a scan speed of 4.0 deg/min.

Surface roughness

The surface roughness (Ra) of the groups was evaluated by using a contact profilometer (Perthometer M2, Mahr GmbH, Göttingen, Germany). Ra values of each specimen were obtained by three measurements on the three different axes passing through the center of the specimens, and mean Ra values were calculated. Measurement parameters were set to nOc: $\times 5$; Oc/L: 0.8; range: 20 \times 5. The profilometer was calibrated before each measurement.

Flexural strength

A three-point bending test was performed to determine the flexural strength of the groups using a universal testing machine (LRX, Lloyd Instruments Ltd., Hampshire, UK) at a crosshead speed of 1 mm/min.

The support distance was set to 8.5 mm, and the loading rod was 2 mm in diameter. The flexural strength was calculated according to the following formula:

$$\sigma = 3NI/2bd^2$$

(σ = flexural strength, N = fracture load [kg/mm²], l = the distance between the supports [8.5 mm], b = width of the specimen [12.5 mm], d = thickness of the specimen [1.2 mm]).

Statistical Analysis

The statistical analysis was performed using SPSS 20 (SPSS Inc., Chicago, IL, USA). Shapiro-Wilks test was used to determine whether the surface roughness and flexural strength data showed normal distribution. Homogeneity of the data was analyzed with Levene's test at the 0.05 significance level. The data were evaluated using three-way ANOVA and post hoc multiple comparison test with Bonferroni correction ($\alpha=0.05$) at a significance level of 0.05. Independent-samples t-test was used to compare the subgroups between the control groups ($P<0.05$).

Results

XRD analysis revealed no monoclinic (m) phase on the surface of the analyzed specimens within groups. Only tetragonal (t) characteristic peaks were determined on the surface of the specimens.

According to the statistical analysis conducted, material, holding time, sintering temperature, and interaction between these factors were not significant for the surface roughness and flexural strength values

Table 2. Univariate comparison of surface roughness (Ra) using three-way ANOVA

Tests for inter-subject effects						
Surface roughness (Ra)	Type III Sum of Squares	df	Mean Square	F	Sig.	
Intercept	44.230	1	44.230	196.449	0.043	
Material	0.223	1	0.223	39.771	0.339	
Sintering temperature	0.033	3	0.011	2.409	0.613	
Holding Time	0.023	3	0.008	0.891	0.635	
Material * Sintering Temperature	0.022	3	0.007	0.553	0.659	
Material * Holding Time	0.035	3	0.012	0.860	0.496	
Sintering Temperature * Holding Time	0.096	9	0.011	0.785	0.638	
Material * Sintering Temperature * Holding Time	0.122	9	0.014	1.851	0.059	

Table 3. Univariate comparison of flexural strength (MPa) values using three-way ANOVA

Flexural strength (MPa)	Tests for inter-subject effects				
	Type III sum of squares	df	Mean square	F	Sig.
Intercept	54981711.760	1	54981711.760	310.425	0.001
Material	95426.642	1	95426.642	23.781	0.768
Sintering Temperature	216660.471	3	72220.157	2.852	0.252
Holding time	147434.274	3	49144.758	2.006	0.339
Material * sintering Temperature	45377.276	3	15125.759	0.595	0.634
Material * Sintering holding time	42920.883	3	14306.961	0.563	0.653
Temperature * holding time	320903.100	9	35655.900	1.402	0.312
Material * sintering temperature * holding time	228969.290	9	25441.032	1.421	0.180

(Tables 2 and 3). Surface roughness values (Ra) obtained from the groups are presented in Table 4 and Figure 1. No significant differences were found between the control group and subgroups in surface roughness values ($P>0.05$). The flexural strength values (MPa) obtained from the groups are presented in Table 5 and Figure 2. No significant differences were found between the control group and subgroups in flexural strength values ($P>0.05$).

Discussion

According to the results of the study, the sintering temperature and holding time did not affect the microstructure, surface roughness, and flexural strength of the groups. Therefore, the null hypothesis of the study that sintering parameters do not affect the microstructure, surface roughness, and flexural strength of the translucent monolithic zirconia was accepted.

Contact profilometers are widely used in the dental field.^{20,21} These devices that provide surface-independent, high-resolution surface profile information, are scientifically accepted.²⁰ Besides, contact profilometers have advantages of repeatability, applicability, and reliability. Therefore, the surface roughness of the specimens was measured using a contact profilometer. Changes in the surface roughness of

materials affect the wear properties of zirconia restorations. This study showed that sintering conditions have no significant effect on the surface roughness of zirconia specimens. Consistent with the present study, Ebeid et al⁹ reported that the mean surface roughness value of zirconia decreased with an increase in sintering temperature and holding time, but these changes were not significant. Preis et al¹⁴ reported no significant difference in surface roughness between the zirconia specimens sintered with different sintering parameters, but the surface roughness of the specimens significantly decreased after glazing and polishing processes; therefore, phase transformation decreased on the surface of zirconia specimens. Surface roughness is associated with bacterial accumulation, and more bacterial involvement occurs on rough surfaces.²² Bollen et al²² reported that the roughness of tooth surface or any restoration should be $<0.2 \mu\text{m}$, and this value could be considered as a threshold value for bacterial involvement. The results of this study revealed that the surface roughness values for all the groups were $>0.3 \mu\text{m}$. These results show that polishing and glazing processes should be performed carefully for zirconia restorations after the sintering process or intraoral adjustment. Phase transformations on the zirconia surface negatively affect the mechanical properties of the material. Mechanical

Table 4. Mean and standard deviation values for surface roughness (Ra)

		Surface Roughness (Ra)	
		Group TZI	Group Up
1400°C	Control	0.36±0.05	0.39±0.1
	30 min.	0.33±0.04	0.34±0.12
	60 min.	0.32±0.04	0.49±0.08
	120 min.	0.36±0.04	0.38±0.08
	240 min.	0.34±0.06	0.39±0.14
1450°C	30 min.	0.36±0.06	0.45±0.13
	60 min.	0.33±0.07	0.38±0.05
	120 min.	0.36±0.05	0.40±0.11
	240 min.	0.36±0.05	0.46±0.11
	30 min.	0.37±0.06	0.40±0.12
1500°C	60 min.	0.37±0.08	0.38±0.13
	120 min.	0.34±0.04	0.44±0.12
	240 min.	0.37±0.04	0.49±0.09
	30 min.	0.37±0.03	0.38±0.12
	60 min.	0.37±0.07	0.35±0.11
1600°C	120 min.	0.37±0.06	0.38±0.13
	240 min.	0.34±0.07	0.43±0.02

Table 5. Mean and standard deviation values for Flexural Strength (MPa)

		Flexural Strength (MPa)	
		Group TZI	Group Up
1400°C	Control	488.50±87.53	586.54±236.32
	30 min.	354.68±126.67	370.23±142.02
	60 min.	407.94±92.97	625.96±187.87
	120 min.	472.48±204.01	427.30±130.20
	240 min.	345.84±94.73	415.18±81.54
1450°C	30 min.	379.96±123.24	489.61±186.61
	60 min.	478.05±177.25	464.12±102.60
	120 min.	414.21±99.34	521.62±179.75
	240 min.	457.53±103.81	433.50±56.88
	30 min.	397.60±90.16	406.28±163.58
1500°C	60 min.	439.63±51.55	510.60±174.54
	120 min.	436.01±75.94	550.28±126.14
	240 min.	435.34±118.11	439.15±79.73
	30 min.	522.95±158.15	490.22±40.02
	60 min.	417.98±51.12	449.28±134.27
1600°C	120 min.	542.80±192.52	545.71±102.84
	240 min.	551.77±119.94	529.04±171.32

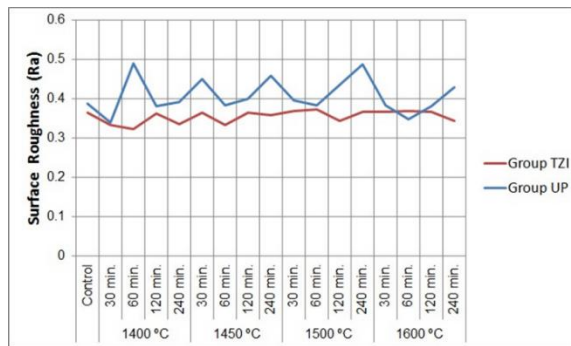


Figure 1. Surface roughness (Ra) changes as a result of changes in the sintering temperature and holding time

properties of zirconia and stability of the tetragonal phase depend on particle size and the metastable microstructure. In this study, sintering temperature and holding time did not affect the phase transformation on the surface of zirconia specimens. Consistent with the present study, Ebeid et al⁹ reported that changing the holding time and sintering temperature did not induce phase transformation on the monolithic zirconia surface. Hjerpe et al⁸ reported no phase transformation in the structure of the partially stabilized zirconia material with a decrease in sintering time. Contrary to the present study, Inokoshi et al²³ investigated the effect of changes in sintering parameters on phase transformation in three different commercial zirconia materials and reported that the cubic phase increased in surface structure due to an increase in sintering temperature and holding time. The authors also reported that as a result of unstable zirconia microstructure, the monoclinic phase was determined at the highest sintering temperature, and changes in sintering parameters caused phase transformation. Differences between the present study and the study conducted by Inokoshi et al²³ could be attributed to higher sintering temperatures used in the previous study.

Zirconia is the most durable ceramic material used in dentistry due to its high flexural strength.^{2,4} According to the results of this study, sintering temperature and holding time did not significantly affect the flexural strength of zirconia specimens. Consistent with the present study, Hjerpe et al⁸ reported that changes in sintering parameters and the thermal aging process did not affect the flexural strength of zirconia. Ebeid et al⁹ concluded that sintering parameters did not significantly affect the flexural strength of the translucent monolithic zirconia material. Contrary to the results of this study, Inokoshi et al²³ reported that changing the sintering parameters affected the mechanical properties of the zirconia material. Trunec²⁴ reported that the fracture strength of zirconia depends on the particle size that varies due to changes in

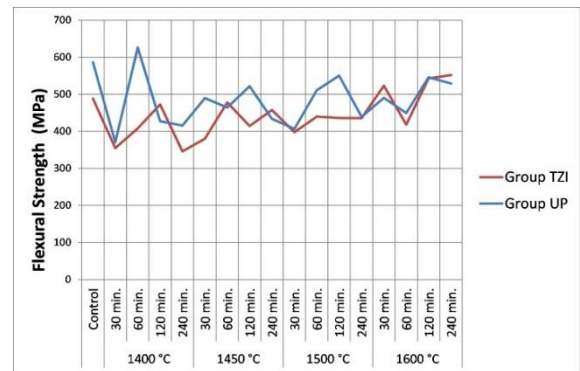


Figure 2. Flexural strength (MPa) changes due to sintering temperature and holding time.

sintering parameters. Stawarczyk et al⁷ concluded that the flexural strength of zirconia decreased with an increase in sintering temperature, and the highest strength could be obtained between 1400°C and 1550°C, and the lowest strength at low temperatures. These differences from other studies could be related to the structure of the material used, sintering parameters, and phase transformation of the material's structure. In this study, the sintering parameters were determined at a certain sintering temperature and holding time intervals in accordance with the literature^{7-9,18,19,23,25} and manufacturer recommendations. Thus, further studies are needed to examine the effect of the sintering process at higher or lower temperatures and in shorter or longer holding times on the properties of zirconia. In addition, the effect of other sintering parameters such as heating rate and sintering atmosphere on the properties of the zirconia should be investigated.

Conclusion

Within the limitations of our study, it was concluded that sintering parameters did not significantly affect the microstructure of translucent monolithic zirconia. Changes in the sintering parameters did not significantly affect the surface roughness of the translucent monolithic zirconia. For all the groups, the surface roughness was above the clinically acceptable values. Changes in sintering parameters did not significantly affect the flexural strength of the translucent monolithic zirconia.

Authors' contributions

CÖ and GC were responsible for the concept and the design of the study. CÖ performed the experimental design of study, data collection and statistical analysis. CÖ and GC were responsible for drafting the manuscript, critical revision of the article and final approval of the version to be published. All the authors participated in the literature review.

Acknowledgments

None.

Funding

This study was not supported financially by any individual or organization.

Competing Interests

The authors declare no competing interests with regards to the authorship and/or publication of this article.

Ethics approval

Not applicable.

References

- Kelly JR, Denry I. Stabilized zirconia as a structural ceramic: an overview. *Dent Mater.* 2008; 24(3):289-98. doi: 10.1016/j.dental.2007.05.005
- Piconi C, Maccauro G. Zirconia as a ceramic biomaterial. *Biomaterials.* 1999; 20(1):1-25. doi: 10.1016/S0142-9612(98)00010-6
- Jang GW, Kim HS, Choe HC, Son MK. Fracture strength and mechanism of dental ceramic crown with zirconia thickness. *Procedia Eng.* 2011;10:1556-60. doi: 10.1016/j.proeng.2011.04.260
- Sundh A, Molin M, Sjögren G. Fracture resistance of yttrium oxide partially-stabilized zirconia all-ceramic bridges after veneering and mechanical fatigue testing. *Dent Mater.* 2005; 21(5):476-82. doi: 10.1016/j.dental.2004.07.013
- Kosmač T, Oblak C, Jevnikar P, Funduk N, Marion L. The effect of surface grinding and sandblasting on flexural strength and reliability of Y-TZP zirconia ceramic. *Dent Mater.* 1999;15(6):426-33. doi: 10.1016/S0109-5641(99)00070-6
- Denry IL, Holloway JA. Microstructural and crystallographic surface changes after grinding zirconia-based dental ceramics. *J Biomed Mater Res B Appl Biomater.* 2006; 76(2):440-8. doi: 10.1002/jbm.b.30382
- Stawarczyk B, Ozcan M, Hallman L, Ender A, Mehl A, Hämmerle CH. The effect of zirconia sintering temperature on flexural strength, grain size and contrast ratio. *Clin Oral Invest.* 2013; 17(1):269-74. doi: 10.1007/s00784-012-0692-6
- Hjerpe J, Vallittu PK, Fröberg K, Lassila LVJ. Effect of sintering time on biaxial strength of zirconium dioxide. *Dent Mater.* 2009; 25(2):166-71. doi: 10.1016/j.dental.2008.05.011
- Ebeid K, Wille S, Hamdy A, Salah T, Etreby A, Kern M. Effect of changes in sintering parameters on monolithic translucent zirconia. *Dent Mater.* 2014; 30(12):e419-24. doi: 10.1016/j.dental.2014.09.003
- Bollen CM, Lambrechts P, Quirynen M. Comparison of surface roughness of oral hard materials to the threshold surface roughness for bacterial plaque retention: a review of the literature. *Dent Mater.* 1997; 13(4):258-69. doi:10.1016/S0109-5641(97)80038-3
- Heintze SD, Cavalleri A, Forjanic M, Zellweger G, Rousson V. Wear of ceramic and antagonist—a systematic evaluation of influencing factors in vitro. *Dent Mater.* 2008; 24(4):433-49. doi: 10.1016/j.dental.2007.06.016
- Teughels W, VAN Assche N, Shiepen I, Quirynen M. Effect of material characteristics and/or surface topography on bio-film development. *Clin Oral Implants Res.* 2006; 17(2):68-81. doi: 10.1111/j.1600-0501.2006.01353.x
- Vagkopoulou T, Koutayas SO, Koidis P, Strub JR. Zirconia in dentistry: Part 1. Discovering the nature of an upcoming bioceramic. *Eur J Esthet Dent.* 2009; 4(2):130-51.
- Preis V, Schmalzbauer M, Bougeard D, Feyrer S, Rosentritt M. Surface properties of monolithic zirconia after adjustment treatments and in vitro wear simulation. *J Dent.* 2015; 43(1):133-9. doi: 10.1016/j.jdent.2014.08.011
- Luthardt RG, Holzner MS, Sandkuhl O, Herold V, Schnapp JD, Kuhlisch E, Walter M. Reliability and properties of ground YTZP-zirconia ceramics. *J Dent Res.* 2002; 81(7):487-91. doi: 10.1177/154405910208100711
- Hallmann L, Ulmer P, Reusser E, Louvel M, Haemmerle CHF. Effect of dopants and sintering temperature on microstructure and low temperature degradation of dental Y-TZP-zirconia. *J Eur Ceram Soc.* 2012;32(16):4091-104. doi:10.1016/j.jeurceramsoc.2012.07.032
- Chevalier J. What future for zirconia as a biomaterial? *Biomaterials.* 2006; 27(4): 535-43. doi:10.1016/j.biomaterials.2005.07.034
- Jiang L, Liao Y, Wan Q, Li W. Effects of sintering temperature and particle size on the translucency of zirconium dioxide dental ceramic. *J Mater Sci: Mater Med.* 2011; 22(11):2429-35. doi: 10.1007/s10856-011-4438-9
- Kim MJ, Ahn JS, Kim JH, Kim HY, Kim WC. Effects of the sintering conditions of dental zirconia ceramics on the grain size and translucency. *J Adv Prosthodont.* 2013; 5(2):161-6. doi: 10.4047/jap.2013.5.2.161
- Frühau J. Problems of contour measuring on microstructures using a surface profiler. *Meas Sci Technol.* 1998; 9(3):293-6.
- Whitehead SA, Shearer AC, Watts DC, Wilson NH. Comparison of two stylus methods for measuring surface texture. *Dent Mater.* 1999;15:79-86. doi: 10.1016/S0109-5641(99)00017-2
- Bollen CM, Lambrechts P, Quirynen M. Comparison of surface roughness of oral hard materials to the threshold surface roughness for bacterial plaque retention: a review of the literature. *Dent Mater.* 1997; 13(4):258-69. doi: 10.1016/S0109-5641(97)80038-3
- Inokoshi M, Zhang F, Munck J, Minakuchi S, Naert I, Vleugels J, Meerbeek BV, Vanmeensel K. Influence of sintering conditions on low-temperature degradation of dental zirconia. *Dent Mater.* 2014; 30(6):669-78. doi: 10.1016/j.dental.2014.03.005
- Trunec M. Effect of grain size on mechanical properties of 3Y-TZP ceramics. *Ceram-Silik.* 2008; 52(3):165-71.
- Stawarczyk B, Frevert K, Ender A, Roos M, Sener B, Wimmer T. Comparison of four monolithic zirconia materials with conventional ones: Contrast ratio, grain size, four-point flexural strength and two-body wear. *J Mech Behav Biomed Mater.* 2016;59:128-38. doi: 10.1016/j.jmbmm.2015.11.040